

# Note on Anisotropy of Resistivity in Hidden Ordered State of URu<sub>2</sub>Si<sub>2</sub>

Kazumasa MIYAKE and Jacques FLOUQUET<sup>1</sup>

*Division of Materials Physics, Department of Physical Science, Graduated School of Engineering Science,*

*Osaka University, Toyonaka, Osaka 560-8531, Japan*

<sup>1</sup>*Commissariat à l'Énergie Atomique, INAC, SPSMS, 17 rue des Martyrs, 38054 Grenoble, France*

(Received October 22, 2009)

KEYWORDS: URu<sub>2</sub>Si<sub>2</sub>, anisotropy of resistivity, hidden order, quadrupolar collective mode

The original form of the so-called hidden order (HO) in URu<sub>2</sub>Si<sub>2</sub> is still debated after its discovery a quarter century ago,<sup>1</sup> while the properties of superconductivity<sup>2–4</sup> and a large-moment antiferromagnetic phase (high-pressure phase)<sup>5,6</sup> have been clarified to some extent. Recently, it has been observed by transport measurement that the resistivity along the *a*-axis,  $\rho_a$ , exhibits a non-Fermi liquid behavior, i.e.,  $\rho_a(T) \propto T$  in the low temperature limit, while that along the *c*-axis,  $\rho_c$ , shows a typical Fermi liquid behavior, i.e.,  $\rho_c(T) \propto T^2$ .<sup>7</sup> This is a note that tries to explain this anisotropy of *T* dependence on the assumption that the hidden order is the induced antiferro (AF)-quadrupolar (Q) order of  $\Gamma_5$  symmetry, i.e.,  $Q_{z(x+y)}$  and  $Q_{z(x-y)}$ . The resulting induced quadrupolar charge distribution is of the  $O_{xy}$  type, which is consistent with a state proposed recently by Harima and the present authors as an ordered state of the HO state.<sup>8</sup> Note that  $[z(x-y)]^2 = z^2(x^2 + y^2 - 2xy)$ . A pattern of the wave function of quadrupolar ordering is shown schematically in Fig. 1. While quadrupolar ordering as an origin of the HO state has already been proposed by Santini and Amoretti,<sup>9</sup> and Ohkawa and Shimizu,<sup>10</sup> the state proposed by Harima *et al.* is consistent with almost all the hidden characteristics of the HO state<sup>8</sup> in contrast to the states proposed thus far.

The fundamental idea is rather simple. The Nambu-Goldstone mode (collective mode in the AF-Q order) scatters electrons in different ways corresponding to the angle between the *c*-axis and the wave vector  $\mathbf{p}$  of quasiparticles. Namely, the coupling constant  $\lambda_{\mathbf{q}}(\mathbf{p})$  between the collective mode with wave vector  $\mathbf{q}$  and an electron with wave vector  $\mathbf{p}$  is given as

$$\lambda_{\mathbf{q}}(\mathbf{p}) = \lambda_{\parallel}(\hat{p}_x Q_{xz,\mathbf{q}} + \hat{p}_y Q_{yz,\mathbf{q}}) + i\lambda_{\perp} q_z \hat{p}_z (Q_{xz,\mathbf{q}} + Q_{yz,\mathbf{q}}), \quad (0.1)$$

where  $\hat{\mathbf{p}} \equiv \mathbf{p}/|\mathbf{p}|$  and  $\lambda_{\parallel}$  and  $\lambda_{\perp}$  are coupling constants that are essentially independent of  $\mathbf{q}$ .

This reflects the fact that long-wavelength fluctuations of quadrupolar moment between two  $\Gamma_5$  states around the equilibrium AF-Q order effectively scatter electrons travelling in the

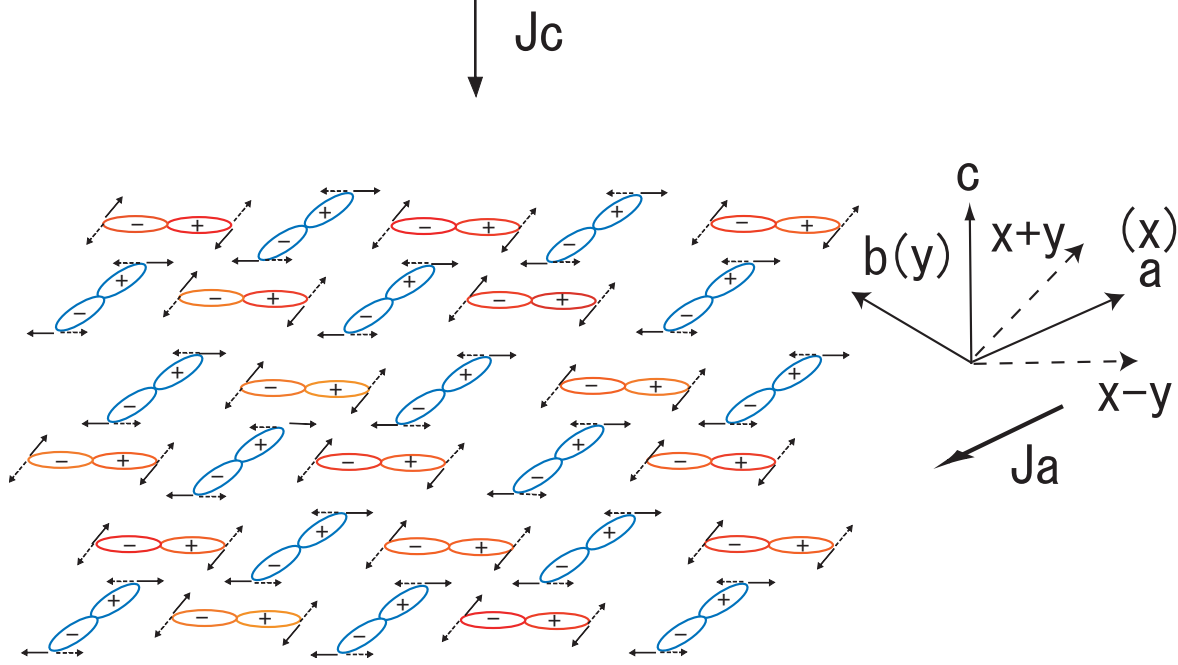


Fig. 1. Coupling between AF-Q collective mode and current of electrons. The arrow of the solid line represents one of the directions of the rotation of induced local quadrupolar moments,  $z(x+y)$  and  $z(x-y)$ , associated with the AF-Q collective mode in the long wavelength limit, and that of the dashed line the inverse direction of local quadrupolar moments. Corresponding to the (0,0,1) order, red and blue dumbbells represent quadrupolar moments in  $c = 0$  and  $c = 1/2$  planes, respectively.

basal plane. On the other hand, these fluctuations give essentially no influence on electrons travelling perpendicular to the basal plane leaving the wave number of electrons intact. These situations can be understood intuitively from a picture shown in Fig. 1. The  $q$ -linear term in the second term of eq. (0.1) represents the fact that the electrons can only be scattered by the difference in the rotation angle (at different lattice sites) of the quadrupolar moments from the equilibrium direction. The absence of the  $q$ -linear term in the first term of eq. (0.1) reflects the fact that even a uniform rotation of quadrupolar moment in the  $ab$ -plane can scatter the electrons travelling in the plane.

Physical and microscopic origins of the couplings are primarily the modulation of the transfer integral of quasiparticles by the fluctuations of quadrupole in the  $ab$ -plane. Figure 2 shows how the transfer integral between adjacent U-sites along the  $a$ -axis among which Ru's are located above or below the  $ab$ -plane including U's. It is easily understood that the transfer of quasiparticles (consisting mostly of  $f$  electrons) via the  $d_{xz}$  orbital of Ru decreases if the  $Q_{xz}$  component of the  $f^1$  configuration of electrons at U ions increases from that of the original orbital shown by dashed lines. This implies that the coupling arises between the quadrupole fluctuation  $Q_{xz,\mathbf{q}}$ , of wave vector  $\mathbf{q}$ , and the electron transfer  $c_{\mathbf{p}+\mathbf{q}}^\dagger c_{\mathbf{p}}$ . This coupling works

even for the uniform variation in  $Q_{xz}$  component at all lattice points. On the other hand, the transfer integral along the  $c$ -axis between two adjacent  $ab$ -planes with the same distribution of U ions (which is not shown in the figure) does not change at all (in the linear approximation of changes in  $Q_{xz}$  component) if the changes in  $Q_{xz}$  component are the same at all lattice points. The coupling arises only from the difference in  $Q_{xz}$  component change between the adjacent  $ab$ -planes. Therefore, the coupling is proportional to  $q_z$  in the long wavelength limit. These facts are represented by the electron-quadrupole interaction Hamiltonian  $H_{e-q}$  as

$$\begin{aligned}
 H_{e-q} = & \sum_{\ell,z} \sum_{(i,j),(x,y)} t'_{ab} \left( Q_{xz} c_{ij\ell}^\dagger c_{i+1,j\ell} + Q_{yz} c_{ij\ell}^\dagger c_{i,j+1,\ell} + \text{h.c.} \right) \\
 & + \sum_{(i,j),(x,y)} \sum_{\ell,z} t'_c \left[ (Q_{xz,\ell} - Q_{xz,\ell+1}) c_{ij\ell}^\dagger c_{ij,\ell+1} \right. \\
 & \left. + (Q_{yz,\ell} - Q_{yz,\ell+1}) c_{ij\ell}^\dagger c_{ij,\ell+1} + \text{h.c.} \right], \quad (0.2)
 \end{aligned}$$

where  $i, j$ , and  $\ell$  denote the lattice coordinates of  $a$ -,  $b$ -, and  $c$ -directions, respectively, and  $t'_{ab}$  and  $t'_c$  are constants parameterizing the changes of transfer integral in the  $ab$ -plane and the  $c$ -direction, respectively. In eq. (0.2), only the hopping terms along the  $a$ -,  $b$ -, and  $c$ -directions are retained.

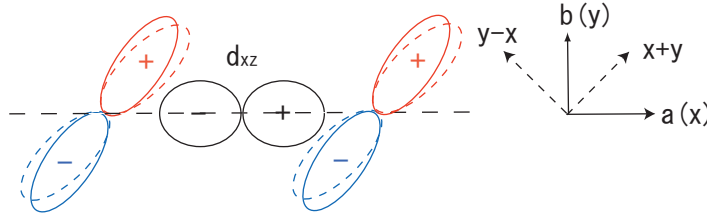


Fig. 2. Schematic view of how the coupling between quadrupole fluctuations of  $Q_{z(x+y)}$  state and quasiparticles arises through modulation of the transfer integral via the  $4d_{xz}$  orbital of Ru's located above or below the  $ab$ -plane including U ions.

The self-energy due to one collective mode exchange process (given by the Feynman diagram shown in Fig. 3) is

$$\Sigma(\mathbf{p}, i\epsilon_n) = T \sum_{\omega_m} \sum_{\mathbf{q}} |\lambda_{\mathbf{q}}|^2 \frac{1}{i\epsilon_n - i\omega_m - \xi_{\mathbf{p}-\mathbf{q}}} \frac{B}{\omega_m^2 + \omega_q^2}. \quad (0.3)$$

After analytic continuation,  $i\epsilon_n \rightarrow \epsilon + i\delta$ , the imaginary part of the retardation self-energy,  $\text{Im}\Sigma^R(\mathbf{p}, \epsilon)$ , is calculated to give

$$\text{Im}\Sigma^R(\mathbf{p}, \epsilon) = -\frac{\pi B}{2} \sum_{\mathbf{q}} \frac{|\lambda_{\mathbf{q}}|^2}{2\omega_q} \left[ \left( \coth \frac{\omega_q}{2T} - \tanh \frac{\epsilon - \omega_q}{2T} \right) \delta(\epsilon - \xi_{\mathbf{p}-\mathbf{q}} - \omega_q) \right]$$

$$+ \left( \coth \frac{\omega_q}{2T} + \tanh \frac{\epsilon + \omega_q}{2T} \right) \delta(\epsilon - \xi_{\mathbf{p}-\mathbf{q}} + \omega_q) \Big]. \quad (0.4)$$

On the Fermi surface, i.e.,  $\mathbf{p} = \mathbf{p}_F$ , and in the limit of  $T \rightarrow 0$ , eq. (0.4) is reduced to

$$\text{Im}\Sigma^R(\mathbf{p}_F, \epsilon) = -\frac{\pi B}{2} \int_0^{|\epsilon|/v_F} \frac{dq}{4\pi^2} \frac{|\lambda_{\mathbf{q}}|^2 q}{\omega_q v_F} \quad (0.5)$$

Assuming the dispersion of the collective mode as  $\omega_q \simeq sq$ , eq. (0.5) is reduced to a rather simple form.

For  $\mathbf{p} \perp c$ ,

$$\text{Im}\Sigma^R(\mathbf{p}_F, \epsilon) = -\frac{B\lambda_{\parallel}^2}{8\pi^2} \frac{1}{sv_F} |\epsilon|/v_F, \quad (0.6)$$

and for  $\mathbf{p} \parallel c$ ,

$$\text{Im}\Sigma^R(\mathbf{p}_F, \epsilon) = -\frac{B\lambda_{\perp}^2}{24\pi^2} \frac{1}{sv_F} (|\epsilon|/v_F)^3. \quad (0.7)$$

Since the scattering by the AF-Q collective mode of wave vector  $(\mathbf{Q}_0 + \mathbf{q})$  couples with the Umklapp process, the temperature dependence of resistivity is given by  $\text{Im}\Sigma^R(\mathbf{p}_F, \epsilon)$ , where  $|\epsilon|$  is replaced by  $T$ . Namely,  $\rho_c \propto T^3$  and  $\rho_a \propto T$ . In the former case, the  $T^3$  dependence is buried in  $T^2$  term of the usual Fermi liquid behavior and will not be observed.

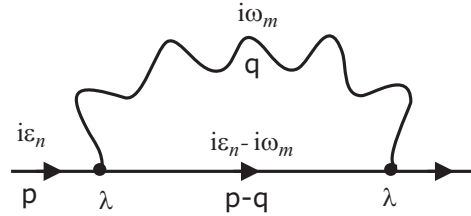


Fig. 3. Feynman diagram for the self-energy due to one-fluctuation mode exchange process.

Thus, the present note shows that the deviation from the  $T^2$  term reported for  $J \parallel a$  is a direct consequence of the nondipolar parameter of the hidden ordered phase. The recent experimental work, which is also given by the current axis, also resolves that in many experiments, the  $T^2$  behavior is not verified even in the temperature region near the superconducting transition temperature  $T_{SC}$ .<sup>11</sup> In agreement with our proposal, under pressures  $P$  higher than  $P_x$ , where the ground state switches from HO to AF, a good  $T^2$  law is absent whatever the current axis ( $a$  or  $c$ ). The difference from the case of AF order is that the coupling with quasiparticles is independent of the wave vector of the quasiparticles in the AF case, while it is highly anisotropic, as shown in eq. (0.1) in the present case of AF-Q order.

In conclusion, we have succeeded in explaining, on an assumption that the HO is an AF-Q order with  $\Gamma_5$  ( $Q_{z(x+y)}$  and  $Q_{z(x-y)}$ ) symmetry, the anisotropy in the temperature dependence of resistivity in the HO phase of  $\text{URu}_2\text{Si}_2$ .

**Acknowledgments**

We are grateful to H. Harima for informative conversations on a possible hidden ordered state supporting our model. This work was supported by a Grant-in-Aid for Specially Promoted Research (20001004) and a Grant-in Aid for Scientific Research on Innovative Areas “Heavy Electrons” (No.20102008) from the Ministry of Education, Culture, Sports, Science and Technology. One of us (J.F.) was supported by the Global COE program from the Japan Society for the Promotion of Science for staying at the Division of Materials Physics, Department of Materials Engineering Science, School of Engineering Science, Osaka University, where this work was initiated.

**References**

- 1) T. Palstra, A. A. Menovsky, J. van Berg, A. J. Dirkmaat, P. H. Kes, G. J. Nieuwenhuys, and J. A. Mydosh: Phys. Rev. Lett. **55** (1985) 2727.
- 2) T. Kohara, Y. Kohori, K. Asayama, Y. Kitaoka, M. B. Maple and M. S. Torikachvili: Solid State Commun. **59** (1986) 603.
- 3) W. Schlabit, J. Baumann, B. Pollit, U. Rauchschwalbe, H. M. Meyer, U. Ahlheim and C. D. Bredl: Z. Phys. B: Condens. Matter **62** (1986) 171.
- 4) Y. Kasahara, T. Iwasawa, H. Shishido, T. Shibauchi, K. Behnia, Y. Haga, T. D. Matsuda, Y. Ōnuki, M. Sigrist, and Y. Matsuda: Phys. Rev. Lett. **99** (2007) 116402.
- 5) G. Motoyama, T. Nishioka and N. K. Sato: Phys. Rev. Lett. **90** (2003) 166402.
- 6) H. Amitsuka, K. Matsuda, I. Kawasaki, T. Tenya and M. Yokoyama: J. Magn. Magn. Mater. **310** (2007) 214.
- 7) Z. Zhu, E. Hassinger, Z. X. Xu, D. Aoki, J. Flouquet and K. Behnia: arXiv:0907.0967.
- 8) H. Harima, K. Miyake, and J. Flouquet: J. Phys. Soc. Jpn. **79** (2010), No.3, in press; arXiv:1001.2369.
- 9) P. Santini and G. Amoretti: Phys. Rev. Lett. **73** (1994) 1027.
- 10) F. J. Ohkawa and H. Shimizu: J. Phys.: Condens. Matter **11** (1999) L519.
- 11) E. Hassinger: private communications.